

Possible new single-buffer layers for $\text{YBa}_2\text{Cu}_3\text{O}_{7-y}$ coated conductors prepared by chemical solution deposition

Author/Contributor:

Li, Guo; Pu, M; Zhou, H; Du, Xi; Zhang, Y; Zhao, Yong

Publication details:

Journal of Materials Research

v. 22

Chapter No. 9

pp. 2398-2403

0884-2914 (ISSN)

Publication Date:

2007

Publisher DOI:

<http://dx.doi.org/10.1557/JMR.2007.0320>

License:

<https://creativecommons.org/licenses/by-nc-nd/3.0/au/>

Link to license to see what you are allowed to do with this resource.

Downloaded from <http://hdl.handle.net/1959.4/38516> in <https://unsworks.unsw.edu.au> on 2023-03-29

Possible new single-buffer layers for $\text{YBa}_2\text{Cu}_3\text{O}_{7-y}$ coated conductors prepared by chemical solution deposition

Guo Li, Minghua Pu, Huaming Zhou, Xiaohua Du, and Yanbing Zhang
Key Laboratory of Advanced Technologies of Materials (Ministry of Education of China),
Superconductivity R&D Center (SRDC), Southwest Jiaotong University, Chengdu,
Sichuan 610031, China

Yong Zhao^{a)}

Key Laboratory of Advanced Technologies of Materials (Ministry of Education of China),
Superconductivity R&D Center (SRDC), Southwest Jiaotong University, Chengdu,
Sichuan 610031, China; and School of Materials Science and Engineering,
University of New South Wales, Sydney 2052 NSW, Australia

(Received 18 August 2006; accepted 14 December 2006)

New single-buffer layers of YBiO_3 and SmBiO_3 have been proposed for $\text{YBa}_2\text{Cu}_3\text{O}_{7-y}$ (YBCO) and $\text{SmBa}_2\text{Cu}_3\text{O}_{7-y}$ coated conductors. Highly *c*-axis oriented YBiO_3 and SmBiO_3 buffer layers have been deposited on single-crystal LaAlO_3 and SrTiO_3 , respectively, by a low-cost chemical solution deposition method in a temperature range as low as 730 to 800 °C in air. Precursor solution of yttrium nitrate, samarium nitrate, and bismuth nitrate has been deposited using spin coating and heat treated in air in a single stage to yield textured YBiO_3 and SmBiO_3 buffers. A very dense, smooth, pinhole-free, and crack-free morphology has been observed for both buffers. Dense, homogeneous, and epitaxially grown YBCO film with thickness about 300 nm has been obtained on YBiO_3 buffer with onset critical temperature 90 K and J_c (77 K, self-field) over 3 MA/cm². These results offer an effective alternative to prepare desirable buffer layer(s) for YBCO-coated conductors.

I. INTRODUCTION

In recent years, the development of second-generation high-temperature superconducting tapes, namely coated conductors, has attracted much attention in the area of the applications of high-temperature superconductivity (HTS).¹⁻⁴ One of the key issues is the preparation of biaxially textured buffer layer(s), which act(s) as a template for the epitaxial deposition of the $\text{YBa}_2\text{Cu}_3\text{O}_{7-y}$ (YBCO) superconductor. In addition to being a diffusion barrier,⁵ the buffer layer provides sufficient crystalline texture to the HTS layer to alleviate the problems related to weak-linked, high-angle grain boundaries.⁶

For YBCO-based coated conductors, many potential buffer layer materials have been identified, including SrTiO_3 , $\text{La}_2\text{Zr}_2\text{O}_7$, CeO_2 , YSZ, and SrRuO_3 , among which an excellent result has been obtained via a three-layered architecture such as $\text{CeO}_2/\text{YSZ}/\text{CeO}_2$.⁷ However, deposition of such a complete buffer layer sequence would involve a combination of both in situ and ex situ

deposition techniques, which could adversely affect the structural and chemical integrity of the individual buffer layers and add to the complexity as well as to the total cost of the overall process, therefore hampering the scale-up of the process. To circumvent these difficulties, it would be of great importance to develop a single-buffer layer deposition technique, which could significantly simplify the preparation and make the fabrication process cost effective and thus facilitate its scale-up to long lengths.

Chemical solution deposition (CSD) such as metal-organic deposition (MOD) and sol-gel process has been demonstrated to offer the desirable aspects of being more easily scalable, inexpensive, and simple. An all-solution approach has been attempted to deposit YBCO coated conductors, which yielded critical current density $J_c > 1 \text{ MA/cm}^2$.⁸⁻¹¹ However, the results obtained by CSD methods are still not as good as that produced by the vacuum processes [pulsed layer deposition (PLD), sputtering, metalorganic chemical vapor deposition (MOCVD), etc.]. One of the main reasons is the relatively poor quality of buffer layer(s), which has high melting point relative to $\text{REBa}_2\text{Cu}_3\text{O}_{7-y}$ (denoted as REBCO, here RE represents rare earth elements except

^{a)}Address all correspondence to this author.

e-mail: yzhao@home.swjtu.edu.cn

DOI: 10.1557/JMR.2007.0320

for Pr, Ce, and Tb), making it difficult to obtain a sufficiently dense buffer layer for the subsequent deposition of superconducting layer. Another drawback of the current CSD process focuses on the great popularity of the expensive metal alkoxides such as butoxides,^{8,9} propoxides,^{10–12} methoxyethoxide,¹³ and metal carboxylates with large hydrocarbon chain such as pentanedionates^{12,14} and naphthenates.¹⁵ Moreover, relatively high annealing temperature as well as reducing atmosphere, which hamper the scale-up of the process, have to be used to obtain well-textured, smooth buffer layer(s). Siegal et al. have reported⁸ a Nb-doped SrTiO_3 buffer layer prepared up to 900 °C in low $P(\text{O}_2)$ ambient. Okuyucu et al. have reported¹² the preparation of RE_2O_3 , which was annealed at 1150 °C in Ar/H_2 4% gas for Ni or Ni–W substrates. Highly textured, smooth, and crack-free $\text{La}_2\text{Zr}_2\text{O}_7$ layer has been obtained by Engel et al.,¹⁶ the annealing has been done at 900 in 5% H_2 -Ar. Akin et al. have succeeded¹⁷ in preparing $\text{CeO}_2/\text{YSZ}/\text{CeO}_2$ architecture via MOD process, while the annealing has been done in 4% H_2 -Ar at up to 950 °C for CeO_2 and 1050 °C for YSZ, respectively. If a new buffer layer material that can be annealed under 800 °C in air or even lower temperature in a reducing atmosphere can be found, it would certainly add to the scalability of the overall process.

In this paper, we propose the new buffer layer materials YBiO_3 for YBCO and SmBiO_3 for SmBCO-coated conductors. REBiO_3 compounds are chosen as the candidate for our study because: (i) the pseudocubic cell of REBiO_3 matches well with the REBCO compounds; (ii) Bi cannot be doped into YBCO lattice,¹⁸ and thus will not suppress its superconductivity; (iii) the melting point of REBiO_3 should be around the center between that of RE_2O_3 (about 2000 °C) and Bi_2O_3 (825 °C). The relatively low melting point of REBiO_3 with respect to those of other buffer materials used currently may lead to a partial melting process for formation of dense textured layer of REBiO_3 at a low processing temperature. Single bismuth yttrium oxide YBiO_3 and bismuth samarium oxide SmBiO_3 buffer layers have been deposited, respectively, via chemical solution deposition process for YBCO-coated conductors. Precursor solution of yttrium nitrate and bismuth nitrate has been spin coated on LaAlO_3 , while samarium nitrate and bismuth nitrate are spin coated on SrTiO_3 . The coated samples were then subjected to heat treatment in air in a temperature range 730 to 800 °C in air. The grown buffer layers yielded a *c*-axis oriented texture. Very dense, smooth, pinhole-free, and crack-free morphology has been observed for both buffers. Dense, homogeneous, and epitaxially grown YBCO film has been deposited on YBiO_3 buffer via a fluorine-free method. Superconducting transition at 90 K and J_c (77 K, self-field) over 3 MA/cm^2 have been achieved.

II. EXPERIMENTAL

Single crystals LaAlO_3 (100) and SrTiO_3 (100), with a dimension of $10 \times 10 \text{ mm}^2$, have been used as substrate. The precursor solution was prepared in ambient atmosphere. The reagents yttrium nitrate (99.9%, Kelong, Beijing, China), samarium nitrate (99.9% Kelong), and bismuth nitrate (99.9%, Kelong) were dissolved in deionized water with continuous stirring. A proper amount of carbamide was then added, which helps to adjust the pH value of the solution. Polyvinyl alcohol (PVA) (home-made) was finally added and stirred for 6 h to adjust the solution viscosity. The final concentration of the solution was 0.25 M. Two solutions were then spin coated on LaAlO_3 and SrTiO_3 single-crystal substrate, respectively, followed by heat treatment in a furnace at 730 to 800 °C for 15 min in air.

YBCO was deposited on the YBiO_3 -buffered LaAlO_3 via a fluorine-free approach developed in our laboratory. During processing, yttrium acetate (99.9%, Kelong), barium acetate (99.9%, Kelong), and cupric acetate (99.9%, Kelong) were dissolved in propionic acid with the cationic ratio $\text{Y}:\text{Ba}:\text{Cu} = 1:2:3.2$. The solution was then spin coated on the YBO -buffered LAO, and the coated sample was dried at 100 to 200 °C. Subsequently, the sample was subjected to 400 to 500 °C to decompose the organic salts. The furnace temperature was then increased to 770 °C and maintained for 3 h for the formation of YBCO phase in Ar. At the end of 3h, the Ar atmosphere was replaced by O_2 with oxygenation at 400 to 450 °C for 0.5 to 4 h.

The as-grown films were characterized using x-ray diffraction (XRD) for phase purity and texture, scanning electron microscopy (SEM) for homogeneity and microstructure, and atomic force microscope (AFM) for crystalline quality and density, as well as roughness. A Philips X'Pert MRD diffractometer (PANalytical, Southwest Jiaotong University, Chengdu, People's Republic of China) with $\text{Cu K}\alpha$ radiation was used to record the θ – 2θ XRD patterns. The microstructure, the crystalline quality, and the roughness samples were analyzed using an SPI3800N AFM (Seiko Instruments Inc., Southwest Jiaotong University, Chengdu, People's Republic of China) and an environmental scanning electron microscope (ESEM) equipped with energy dispersive spectroscopy (EDS). Superconducting transition and the hysteresis loops of $M(H)$ were measured by using Quantum Design (Southwest Jiaotong University, Chengdu, People's Republic of China) SQUID XL (7T).

III. RESULTS AND DISCUSSION

Bismuth yttrium oxide, YBiO_3 , has a cubic structure as shown in Fig. 1, with lattice parameter $a = 5.428 \text{ \AA}$ and pseudocubic cell with $a' = 3.838 \text{ \AA}$, which is closely matched to that of the orthorhombic YBCO (1% mismatch with a_{YBCO} and 0.5% mismatch with b_{YBCO}).

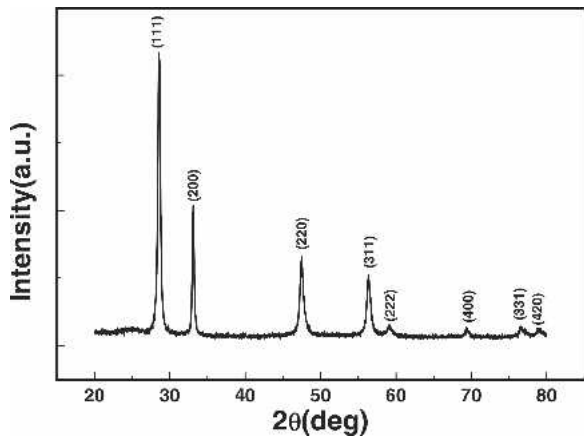


FIG. 1. Typical powder θ - 2θ XRD pattern of YBiO_3 .

SmBiO_3 has an identical cubic structure, except that the lattice parameter $a = 5.536 \text{ \AA}$ and pseudocubic cell with $a' = 3.914 \text{ \AA}$ (0.07% mismatch with a_{SmBCO} and 1.5% mismatch with b_{SmBCO}). No phase transition has been observed from room temperature up to $1050 \text{ }^\circ\text{C}$ through the XRD powder diffraction for the two buffers.

A typical XRD θ - 2θ scan for the YBO layer deposited

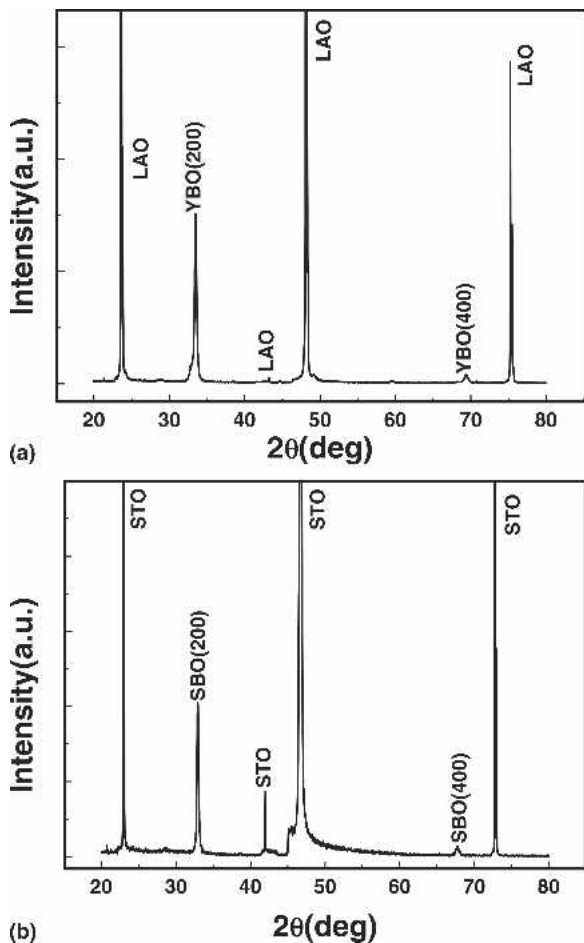


FIG. 2. Typical θ - 2θ XRD pattern of: (a) $\text{YBiO}_3/\text{LaAlO}_3$, and (b) $\text{SmBiO}_3/\text{SrTiO}_3$, showing a good c -axis texture of YBiO_3 and SmBiO_3 .

on LaAlO_3 single-crystal substrate is given in Fig. 2(a), which reveals the presence of a sharp out-of-plane texture for the YBiO_3 buffer layer. It is obvious that the intensities of the (111) peak of YBiO_3 buffer layer is negligible compared with the intensity of its (200) peak. Figure 2(b) displays the phase and texture information for SmBiO_3 buffer on SrTiO_3 . The SmBiO_3 film exhibits an ($n00$) texture except for a tiny trace of undesirable (111) peak. This suggests that these buffer layers have a strong tendency toward preferred orientation. As a matter of fact, one of the starting materials, Bi_2O_3 melts at $817 \text{ }^\circ\text{C}$ under ambient atmosphere as we used in our experiment. Therefore, upon heating after decomposition, the mixtures of Y_2O_3 and Bi_2O_3 (or Sm_2O_3 and



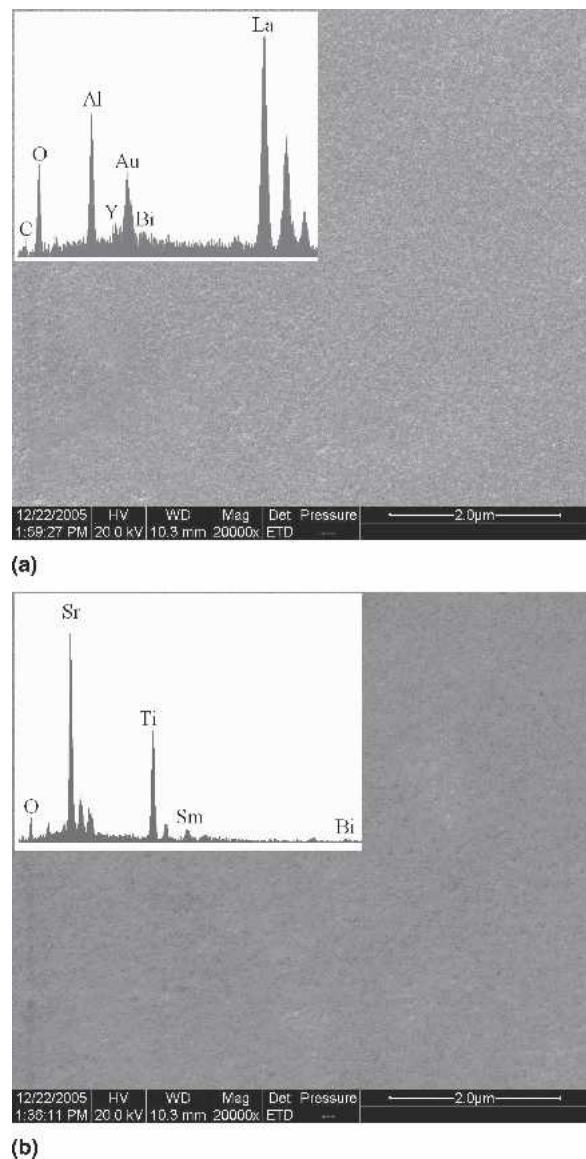


FIG. 3. SEM micrograph of buffer layers: (a) YBiO_3 deposited on LaAlO_3 single-crystal substrate, and (b) SmBiO_3 buffer layer deposited on SrTiO_3 single-crystal substrate. Insets show the results of EDS analyses for the Y, Sm, and Bi concentrations.

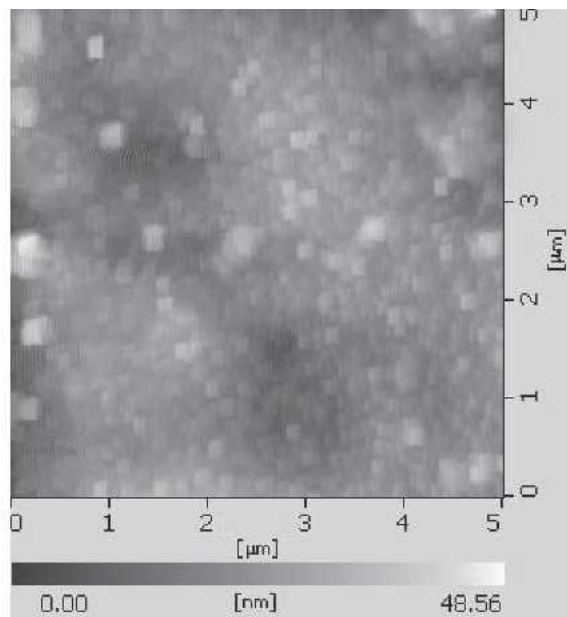

(a)

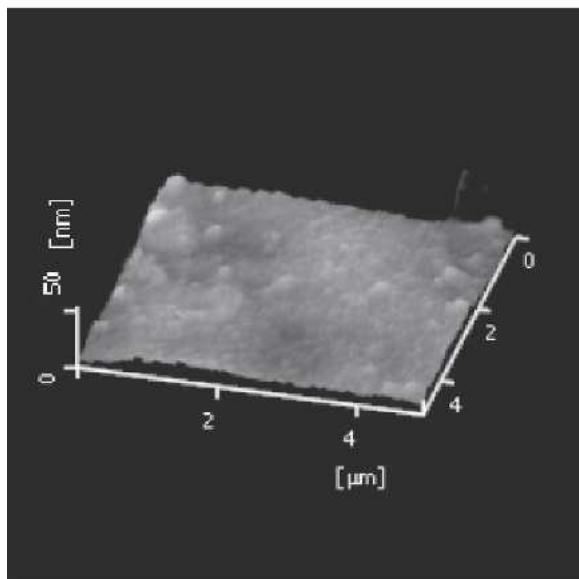


(b)


FIG. 4. Surface cut-out ($5 \mu\text{m} \times 5 \mu\text{m}$) of YBiO_3 buffer layer on LaAlO_3 measured by AFM.

Bi_2O_3) will undergo a partial melting process. Similar to the melt texture growth (MTG) process used for REBCO, this partial melting process is likely to lead to preferred orientation, with the LaAlO_3 (SrTiO_3) substrate serving as a big seed layer.

In addition to the excellent crystalline quality, YBiO_3 and SmBiO_3 layers show a dense, homogeneous, crack-free, and pinhole-free microstructure, as displayed in Figs. 3(a) and 3(b), respectively. A pebble-like morphology, with an approximate grain size of 50 nm has been observed for YBiO_3 , which can be interpreted as corresponding to good c -axis texture, while for SmBiO_3 buffer

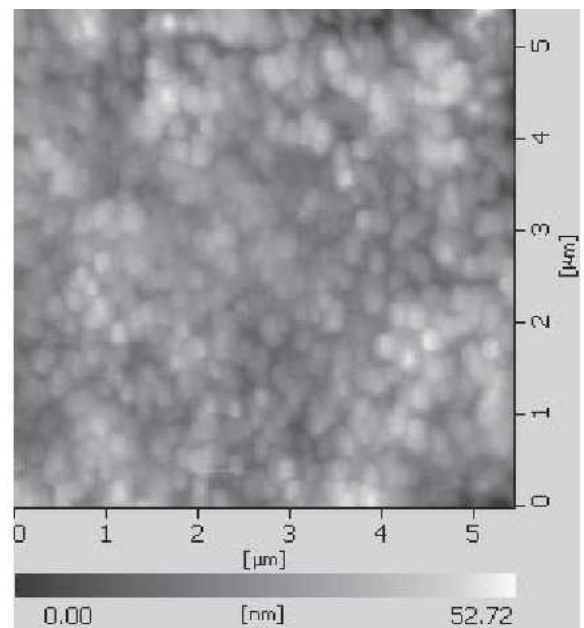

(a)

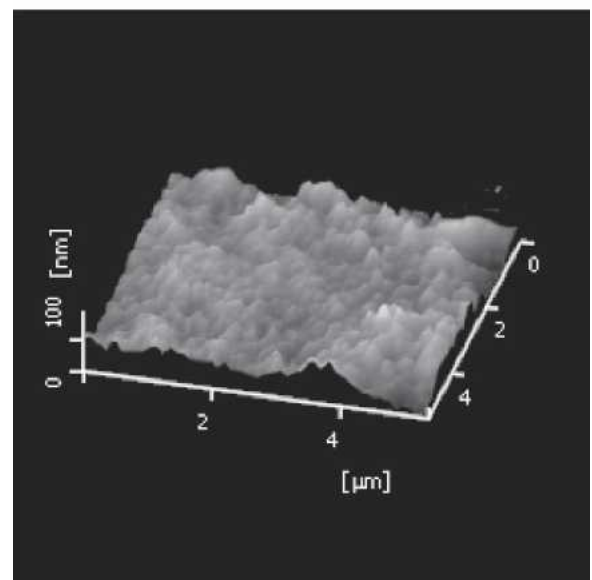

(b)

FIG. 5. Surface cut-out ($5 \mu\text{m} \times 5 \mu\text{m}$) of SmBiO_3 buffer layer on SrTiO_3 measured by AFM.

layer, the grains are still finer. Qualitative EDS analysis reveals a very good distribution of the cations with a ratio $\text{Y}(\text{Sm}):\text{Bi} \approx 1:1$. AFM investigations of the surface structure of the buffer layers YBO and SBO point toward a homogeneous granular structure, as shown in Figs. 4 and 5. The root-mean-square roughness of YBiO_3 buffer layer is about 5 nm and that of SmBiO_3 is about 9 nm, which indicates a relatively smooth surface of the buffer systems, which is important for a successful epitaxial growth of c -axis aligned YBCO layer. The effect of the densification obtained by SEM images can equally be confirmed.

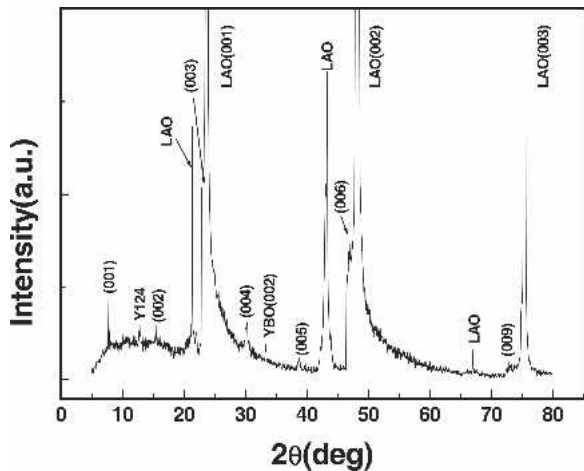


FIG. 6. Typical θ - 2θ XRD pattern of YBCO/YBiO₃/LaAlO₃ showing the good *c*-axis texture of YBCO.

The morphology observed above results on one hand from the careful control of the thermal process and on the other hand from the partial melting process, the latter due to the relative low melting temperature of Bi_2O_3 , facilitating the densification of YBiO₃ (SmBiO₃). As a matter of fact, it is possible that Bi_2O_3 undergoes a partial melting process, which may be favorable for the solid solution YBiO₃ (SmBiO₃) to obtain a better density, i.e., a better densification of YBiO₃ (SmBiO₃). Moreover, the melting point of the final product YBiO₃ (SmBiO₃) has been proved to be well above 1050 °C through a differential thermal analysis (DTA) process, which means that the partial melting process will exert little influence on the subsequent YBCO layer. As we mentioned previously, the prevailing buffer layer materials including SrTiO₃, La₂Zr₂O₇, CeO₂, YSZ, SrRuO₃, etc., are all heritages from those used in the former physical process. In

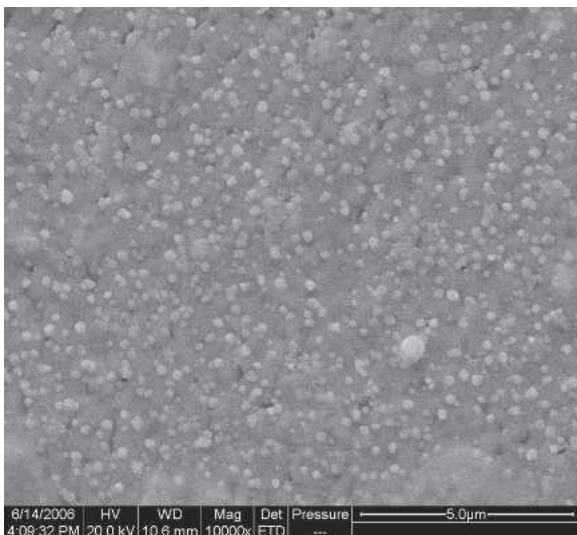


FIG. 7. SEM micrograph of YBCO layer deposited on YBiO₃-buffered LaAlO₃ single-crystal substrate showing good density and surface morphology.

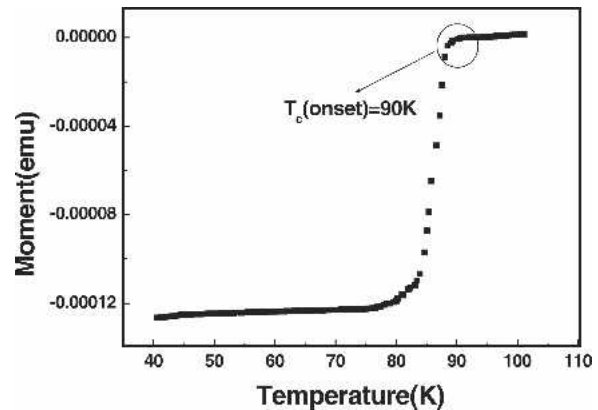


FIG. 8. Temperature dependence of magnetic moment for YBCO/YBiO₃/LaAlO₃ yielding an onset critical temperature 90 K.

the in situ vacuum process, densification can be easily ensured because of the layer-by-layer route, whereas in the nonvacuum CSD process, densification seems to have greatly hampered its scale-up and remains a problem. The introduction of a new compound Bi_2O_3 , with its relative low melting point, offers a new approach to densify the buffer layer and facilitate the deposition of superconducting layer.

In addition to the densification effect, the introduction of Bi_2O_3 has decreased the process temperature by 150 to 300 °C. YBiO₃ and SmBiO₃ can be prepared at 730 to 800 °C, which makes the process cost effective and easily scaled up.

The YBCO layer with a thickness of about 300 nm deposited on YBiO₃-buffered LaAlO₃ shows a highly developed *c*-axis texture as in Fig. 6, though there may exist Y-124, which may due to the relatively low annealing temperature. A dense, homogeneous, crack-free, and pinhole-free microstructure has been observed, as shown in Fig. 7. Figure 8 shows the superconducting transition

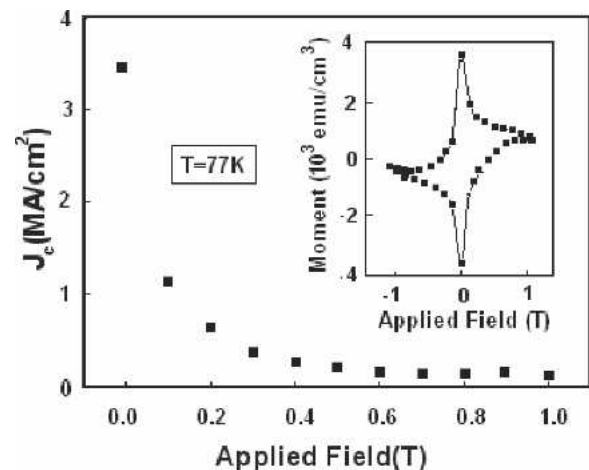


FIG. 9. Field dependence of critical current density at 77 K and self-field for YBCO films deposited on YBiO₃ buffered LaAlO₃. Inset: Hysteresis loop of magnetization at 77 K.

of the YBCO, which starts at 90 K. The sharp superconductivity transition of the YBCO film demonstrates a high quality and phase uniformity of the film. The critical current density deduced from the hysteresis loops of $M(H)$ curves is more than 3 MA/cm^2 at 77 K in self-field, demonstrating a high performance of the superconducting layer (see Fig. 9).

A YBiO_3 buffer has also been deposited on untextured Ni substrates in Ar/H_2 4% gas. Unlike when processing in air, the processing temperature for YBiO_3 phase formation is decreased to as low as 700°C in the reducing ambient. At the same time, no chemical reaction between YBiO_3 and Ni substrate was observed, demonstrating that the new buffer materials and related processing are very metal-friendly. This result, together with the formation of a highly textured YBiO_3 film on LaAlO_3 single-crystal substrate, strongly suggests that YBiO_3 should be a good candidate as a buffer material for Ni-substrate-based YBCO coated conductors prepared by an all-solution method.

IV. CONCLUSION

New materials YBiO_3 and SmBiO_3 have been proposed to be deposited as a single buffer layer for YBCO and SmBCO coated conductors. YBiO_3 and SmBiO_3 layer have been deposited, respectively, on LaAlO_3 and SrTiO_3 single-crystal substrates via a chemical solution deposition route. In addition to the excellent c -axis texture of these buffer layers, a very dense, homogeneous, crack-free and pinhole-free microstructure has been observed. The subsequently deposited YBCO film with a thickness about 300 nm on YBiO_3 shows good c -axis texture, excellent surface morphology, and high superconducting performance. The introduction of Bi_2O_3 has been argued to be mainly responsible for the amelioration of the densification as well as the decrease of the process temperature, which is more metal-friendly. This approach offers an alternative for densifying the buffer layer.

ACKNOWLEDGMENTS

The authors would like to thank R. Shen for XRD experiments, C.X. Jiang for SEM measurements, and L. Gong for AFM analysis. The authors are also grateful to National Natural Science Foundation of China (Grant Nos. 50372052, 50430137, 50588201), Specialized Research Fund for the Doctoral Program of Higher Education of China (Grant No. 20040613027), Southwest Jiaotong University R&D Program (Grant No. 2004A02), and Australian Research Council (Grant Nos. DP0452522, DP0559872) for the financial support.

REFERENCES

1. A.P. Malozemoff, S. Annavarapu, L. Fritzeimer, Q. Li, V. Prunier, M. Rupich, C. Thieme, W. Zhang, A. Goyal, M. Paranthaman, and D.F. Lee: Low-cost YBCO coated conductor technology. *Supercond. Sci. Technol.* **13**, 473 (2000).
2. D.P. Norton, A. Goyal, J.D. Budai, D.K. Christen, D.M. Kroeger, E.D. Specht, Q. He, B. Saffian, M. Paranthaman, C.E. Klabunde, D.F. Lee, B.C. Sales, and F.A. List: Epitaxial $\text{YBa}_2\text{Cu}_3\text{O}_7$ on biaxially textured nickel (001): An approach to superconducting tapes with high critical current density. *Science* **274**, 755 (1996).
3. L.R. Motowidlo, V. Selvamanickam, G. Galinski, N. Vo, P. Haldar, and R.S. Sokolowski: Recent progress in high-temperature superconductors at Intermagnetics General Corporation. *Phys. C* **335**, 44 (2000).
4. T. Watanabe, H. Iwai, T. Muroga, S. Miyata, Y. Yamada, and Y. Shiohara: Advances in coated conductor development at SRL-Nagoya Coated Conductor Center. *Phys. C* **412**, 819 (2004).
5. J.M. Phillips: Substrate selection for high-temperature superconducting thin films. *J. Appl. Phys.* **79**, 1829 (1996).
6. S.E. Babcock, X.Y. Cai, D.L. Kaiser, and D.C. Larbalestier: Weak-link-free behavior of high-angle $\text{YBa}_2\text{Cu}_3\text{O}_{7-8}$ grain boundaries in high magnetic-fields. *Nature* **347**, 167 (1990).
7. J.E. Mathis, A. Goyal, D.F. Lee, F.A. List, M. Paranthaman, D.K. Christen, and E.D. Specht: Biaxially textured $\text{YBa}_2\text{Cu}_3\text{O}_{7-8}$ conductors on rolling assisted biaxially textured substrates with critical current densities of 2–3 mA/cm(2). *Jpn. J. Appl. Phys.* **37**, L1379 (1998).
8. M.P. Siegal, P.G. Clem, J.T. Dawley, R.J. Ong, M.A. Rodriguez, and D.L. Overmyer: All solution-chemistry approach for $\text{YBa}_2\text{Cu}_3\text{O}_{7-8}$ -coated conductors. *Appl. Phys. Lett.* **80**, 2710 (2002).
9. S. Sathyamurthy and K. Salama: Chemical solution deposition of highly oriented strontium titanate buffer layers for coated conductors. *Supercond. Sci. Technol.* **13**, L1 (2000).
10. S. Sathyamurthy, M. Paranthaman, and H.Y. Zhai: Lanthanum zirconate: A single buffer layer processed by solution deposition for coated conductor fabrication. *J. Mater. Res.* **17**, 2181 (2002).
11. S. Sathyamurthy, M. Paranthaman, H.Y. Zhai, S. Kang, H.M. Christen, C. Cantoni, A. Goyal, and P.M. Martin: Solution processing of lanthanum zirconate films as single buffer layers for high I-c YBCO coated conductors. *IEEE Appl. Supercond.* **13**, 2658 (2003).
12. H. Okuyucu, L. Arda, Y. Akin, Z.K. Heida, Z. Aslanoglu, and Y.S. Hascicek: Development of 100% lattice match buffer layers on RABiTS Ni tapes by sol-gel. *IEEE Appl. Supercond.* **13**, 2680 (2003).
13. M. Paranthaman, T.G. Chirayil, S. Sathyamurthy, D.B. Beach, A. Goyal, F.A. List, D.F. Lee, X. Cui, S.W. Lu, B. Kang, E.D. Specht, and P.M. Martin: Fabrication of long lengths of YBCO coated conductors using a continuous reel-to-reel dip-coating unit. *IEEE Appl. Supercond.* **11**, 3146 (2001).
14. E. Celik and Y.S. Hascicek: Texturing influence of process parameters in sol-gel Tb_2O_3 buffer layers on Ni tapes for YBCO coated conductors. *Mater. Sci. Eng., B* **96**, 300 (2002).
15. A. Takechi, K. Matsumoto, and K. Osamura: Oxide buffer layer with perovskite structure for $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ coated conductors prepared by metal-organic deposition method. *IEEE Appl. Supercond.* **13**, 2551 (2003).
16. S. Engel, K. Knoth, R. Huhne, L. Schultz, and B. Holzapfel: An all chemical solution deposition approach for the growth of highly textured CeO_2 cap layers on $\text{La}_2\text{Zr}_2\text{O}_7$ -buffered long lengths of biaxially textured Ni-W substrates for YBCO-coated conductors. *Supercond. Sci. Technol.* **18**, 1385 (2005).
17. Y. Akin, Z. Aslanoglu, E. Celik, L. Arda, W. Sigmund, and Y.S. Hascicek: Textured growth of multi-layered buffer layers on Ni tape by sol-gel process. *IEEE Trans. Appl. Supercond.* **13**, 2673 (2003).
18. F. Delorme, C. Harnois, and I. Monot-Laffez: Bismuth doping of top-seeding melt-texture-grown $\text{YBa}_2\text{Cu}_3\text{O}_{7-8}$ ceramics. *Supercond. Sci. Technol.* **16**, 739 (2003).